



Original Research Article

Phytofabrication, and Characterization of Ag/Fe₃O₄ Nanocomposite from *Rosa Canina* Plant Extracts Using a Green Method

Nasrin Pourbahar^{a,*} , Somayeh Sattari Alamdar^b 

^a Department of Chemistry, Faculty of Science, Ilam University, P.O. Box 69315516, Ilam, Iran

^b Department of Organic Chemistry Faculty of Pharmaceutical Chemistry Tehran Medical Science Islamic Azad University, Tehran, Iran

ARTICLE INFORMATION

Received: 3 January 2023
Received in revised: 18 January 2023
Accepted: 21 January 2023
Available online: 28 January 2023

DOI: 10.22034/ajgc.2023.1.2

KEYWORDS


Green synthesis
Ag/Fe₃O₄-MNPs
Rosa Canina

ABSTRACT

In this study, the Ag/Fe₃O₄ nanocomposite was prepared by *Rosa Canina* fruit extract as a suitable reducing source and stabilizing agent. The green synthesized nanostructure was characterized using UV-visible, X-ray diffraction analysis (XRD), field emission scanning electron microscope (FE-SEM), energy-dispersive X-ray spectroscopy (EDX), Fourier-transform infrared spectroscopy (FT-IR), and vibrating-sample magnetometer (VSM) techniques. TEM analysis of Ag/Fe₃O₄ nanocomposite showed a spherical shape (MNPs) with an average size of 8–28 nm.

© 2023 by SPC (Sami Publishing Company), Asian Journal of Green Chemistry, Reproduction is permitted for noncommercial purposes.

Graphical Abstract

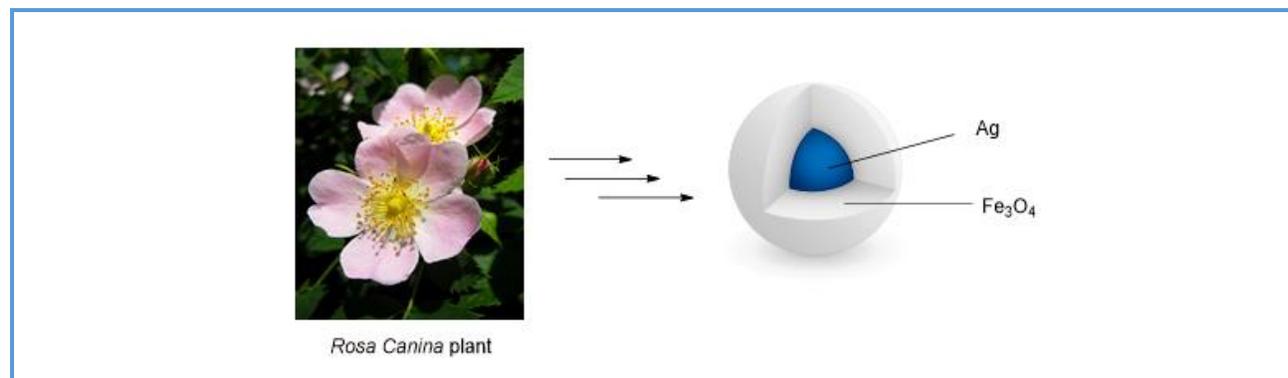

Introduction

Research in the field of nanotechnology is growing rapidly due to their unique properties and their use in a wide range of applied programs in various sciences such as biological, chemical, and industrial sciences is expanding. The role of nanoparticles is increasing for use in cancer diagnosis, treatment, and the design of advanced drug delivery systems. Nanoparticles can be a potential alternative for treating diseases. Among the most important and widely used of these materials are silver nanoparticles [1].

Currently, it is believed that silver nanoparticles can be used as a therapeutic agent, in addition to be used in the fight against bacteria and the effect on wound healing, to fight against AIDS and viruses [2-5]. Likewise, Iron oxide nanoparticles are the foremost nanoscale materials with many practical applications such as biosensors, catalysts, and environmental remediation [6]. It plays a central role in a wide range of biomedical applications such as cell therapy, tissue engineering, drug delivery, photothermal effect, regenerative medicine, hyperthermia, and diagnosis [7-9]. There are several reports on the synthesis of magnetic nanoparticles where different reducing agents such as hydrazine, dimethylformamide, sodium borohydride, and carbon monoxide [10-14], etc. were used. These reducing agents are highly reactive chemicals that have adverse effects on the environment and hinder the biocompatibility of magnetic nanoparticles, which leads to the limited biomedical applications of chemically reduced magnetic nanoparticles. To use magnetic nanoparticles in biomedical applications, they should be strictly biocompatible. Therefore, novel and environmentally friendly, biogenic reduction/greener synthesis methods are highly sought. Biogenic reduction methods

which include the use of fungi, bacteria, and plant extracts, can be one of the best options to opt for the nanoparticles synthesis. Such greener methods are environment-friendly, cost-effective, provide good yield, and have decent reproducibility [15]. The availability of biogenic reductive materials in nature makes them a promising candidate for the nanoparticles synthesis. Such greenly synthesized biocompatible magnetic nanoparticles are particularly useful for magnetic separation of enzymatic catalysis for reuse [16]. Studies have shown that the bactericidal activity of transition metal NPs can be attributed to many different properties, the most important being the ability to generate ROS and their affinity to associate closely with R-SH groups [17, 18]. Today, drug-resistant bacteria have created serious problems in the treatment of many infectious diseases. Consequently, finding new ways to fight against these pathogens are important. Therefore, recent studies have focused on the study of the antimicrobial effects of plant origin [19]. The aim of this work is to synthesize the Ag/Fe₃O₄ nanocomposite using an aqueous extract of *Rosa Canina* fruit as a reducing agent and stabilizer.

Experimental

Materials and methods

All chemicals were of analytical grade purity and used as received. Ferric chloride hexahydrate, ferrous chloride tetrahydrate, ammonia solution (25%), were purchased from Merck company.

Preparation of Rosa Canina fruit extract

20 g of dried powder of the *R. Canina* fruit was mixed with 100 mL of solvent (ethanol-water (1:1)). The mixture was stirred in a

shaker at 150 rpm away from light at room temperature for 48 h. The supernatant phase was removed and centrifuged 3 times at 3000 rpm for 10 minutes, and then filtered. After evaporating the solvent, the extract obtained through this method was poured into a glass container and stored at 255 K.

Preparation of the Ag/Fe₃O₄ nanocomposite

100 mL of 5000 ppm *Rosa Canina* fruit extract was taken in a 250 two-neck round bottom flask, and then 4 mmol Fe₂(SO₄)₃·4H₂O, 2 mmol FeSO₄·7H₂O, and 1.5 mmol AgNO₃ were added. After that, 10 ml of 9 M ammonia solution was injected dropwise into the mixture with vigorous stirring under N₂ atmosphere for 1 h at 333 K. The resultant solution was a dark brown color precipitate. The precipitate was separated by applying external magnetic field and washed with water for several times as well as dried in oven at 333 K for 24 h.

Results and Discussion

Figure 1 displays the UV-visible spectrum of *Rosa Canina* fruit extract. This spectrum shows bonds at λ_{\max} 297 nm and 321 nm due to the transition localized within the ring of the benzoyl system and the cinnamoyl system, respectively. These bonds could be attributed to

$\pi \rightarrow \pi^*$ transitions of the extract's aromatic system of phenolic compounds.

The UV-visible spectrum of the green synthesized Ag/Fe₃O₄ nanocomposite using the aqueous extract of *Rosa Canina* is depicted in Figure 2. The surface plasmon resonance (SPR) peak is centered at 421 nm which is demonstrating the nanocomposite formation.

Figure 3 demonstrates the X-ray diffraction pattern of the Ag/Fe₃O₄ nanocomposite. The patterns at 2θ values 38.1°, 44.3°, 64.4°, and 77.2° can be assigned to (111), (200), (220), and (311) crystal planes in Ag cubic structure which agree with the standard Ag (JCPDS 04-0783) [20]. The diffraction peaks at $2\theta = 30.3^\circ, 35.7^\circ, 43.2^\circ, 57.3^\circ,$ and 63.03° can be indexed to (220), (311), (400), (511), and (440) planes of cubic Fe₃O₄ (JCPDS 19-0629), offering the formation of Fe₃O₄ particles [21]. The average size of the Ag/Fe₃O₄ nanocomposite was calculated using the Scherrer equation:

$$d = k \lambda / \beta \cos \theta$$

Where, d is the particle size of the crystal, k is Scherrer constant, λ is X-ray wavelength, β is the width of the XRD peak at half height, and θ is the Bragg diffraction angle. The average crystalline size of the Ag/Fe₃O₄ nanocomposite is calculated at 33 nm.

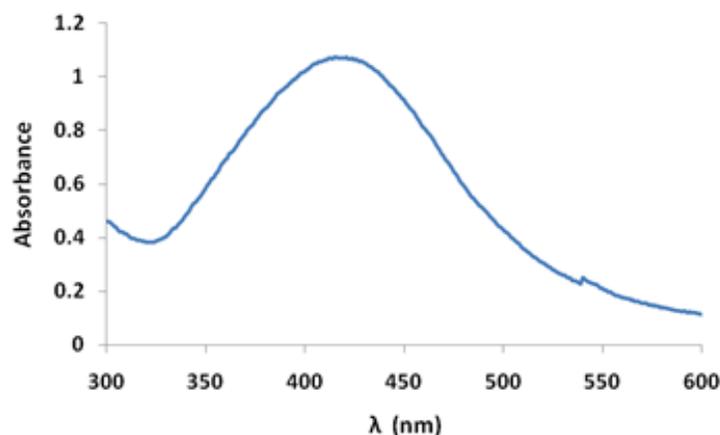


Figure 1. A UV-visible spectrum of *Rosa Canina* fruit extract

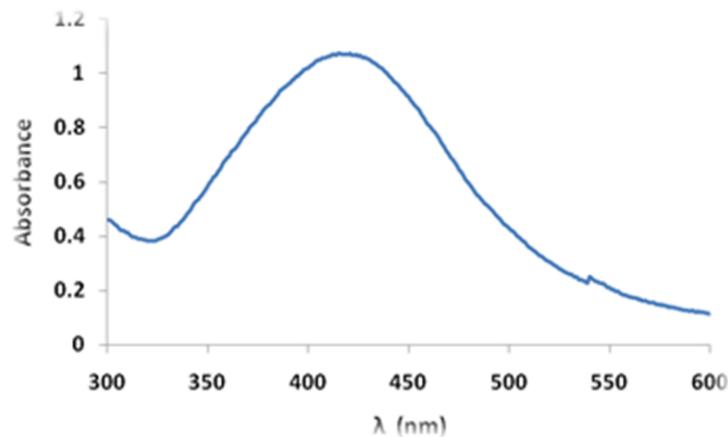


Figure 2. The UV-visible spectrum of Ag/Fe₃O₄ nanocomposite using *Rosa Canina* fruit extract

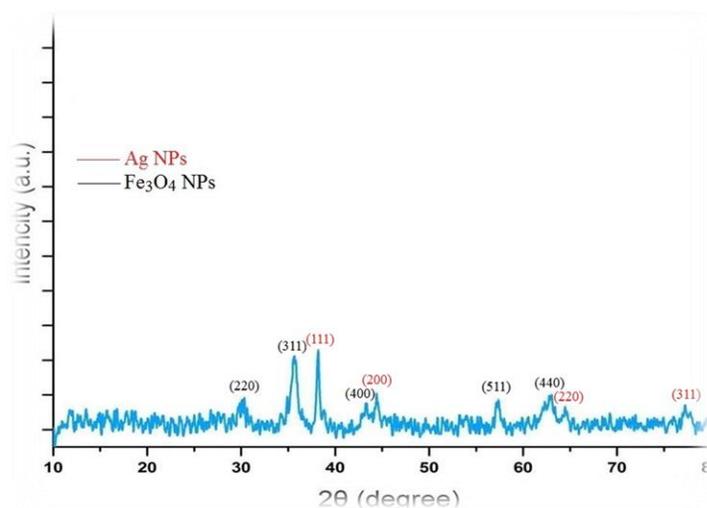


Figure 3. The XRD powder pattern of Ag/Fe₃O₄ nanocomposite

The FT-IR analysis was performed to recognize the possible biomolecules responsible for the reduction of the metal ions and capping of the bio-reduced nanoparticles. The FT-IR spectra of the *Rosa Canina* fruit extract and the Ag/Fe₃O₄ nanocomposite are illustrated in Figure 4. The FT-IR spectrum of the extract (Figure 4a) represented a broad peak at 3500 to 3000 which is attributed to free OH in the molecule and OH group forming hydrogen bonds [22]. The peaks at 1634, 1412, and 1098 cm⁻¹ in the spectrum of the extract represented a carbonyl group (C=O), stretching C=C aromatic ring, and C-OH stretching

vibrations, respectively. These peaks could be ascribed to the presence of flavonoids and other phenolic compounds in the *Rosa Canina* fruit extract as responsible for the bioreduction of metal ions. Actually, the π -electrons of the carbonyl group of phenolic compounds in a Red/Ox mechanism can transfer to the free orbital of metal ions and change them to the zero-valent. The FT-IR spectrum of the Ag/Fe₃O₄ nanocomposite (Figure 4b), in addition to the peaks of phenolic compounds in the extract, represented the characteristic peak of Fe-O at 583 and 468 cm⁻¹, respectively [23].

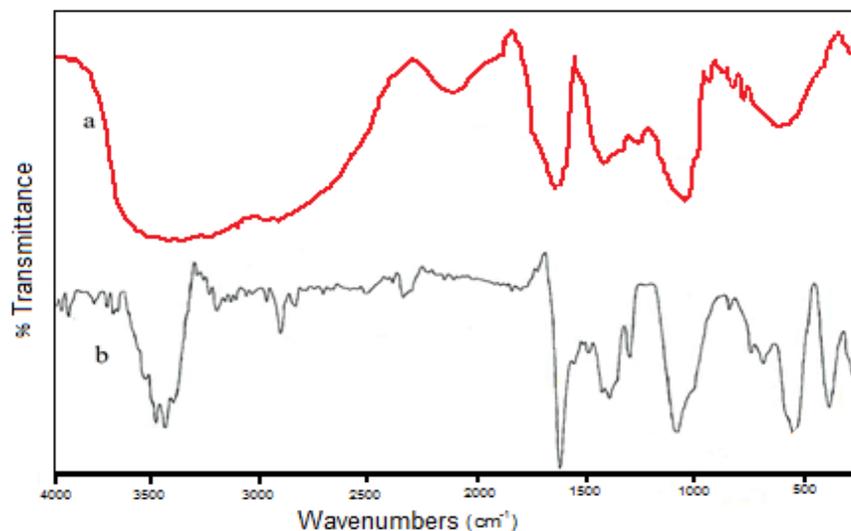


Figure 4. FT-IR spectra of (a) *Rosa Canina* fruit extract and (b) Ag/Fe₃O₄ nanocomposite

The morphology of Ag/Fe₃O₄ nanocomposite is revealed by field emission scanning electron microscopy (FE-SEM). FE-SEM analysis of the magnetic nanocomposite showed uniform-sized particles with spherical morphology (Figure 5).

Elemental analysis of synthesized nanocomposite (Ag/Fe₃O₄) was performed using the EDS technique. As demonstrated in (Figure 6), Fe, O, and Ag peaks indicate a

successful synthesis. Furthermore, the presence of peak carbon in the EDS spectrum indicates the presence of organic compounds in a plant extract at the nanoscale.

TEM was another technique we applied to confirm the morphology of the Ag/Fe₃O₄ MNPs. In Figure 7, The transmission electron microscope image reveals the size of synthesized nanocomposite to be less than 30 nm.

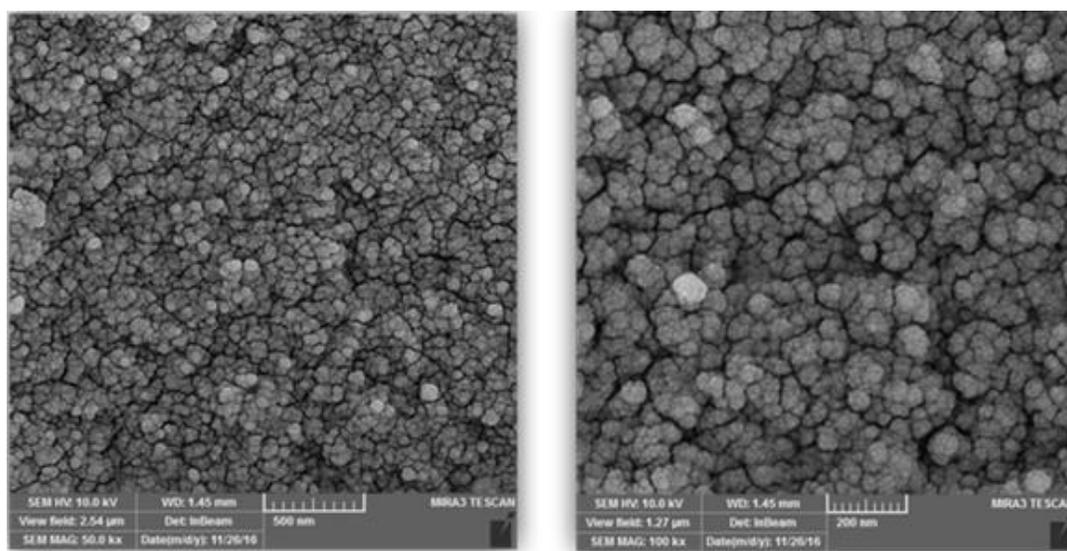


Figure 5. FE-SEM images of Ag/Fe₃O₄ nanocomposite

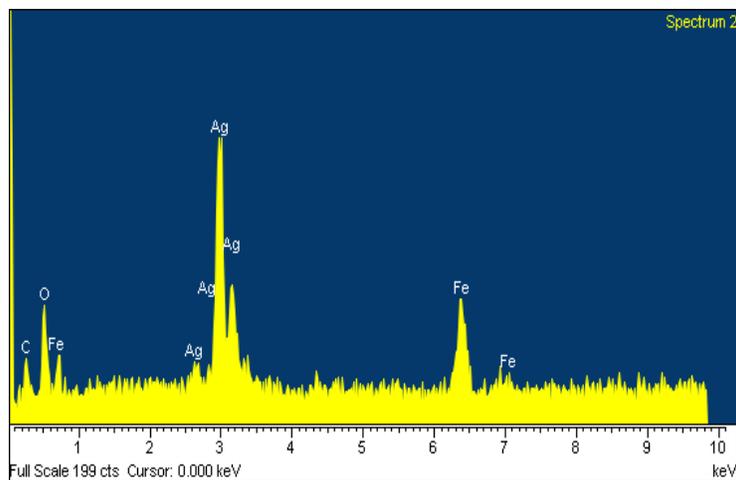


Figure 6. EDS image of the Ag/Fe₃O₄ MNPs

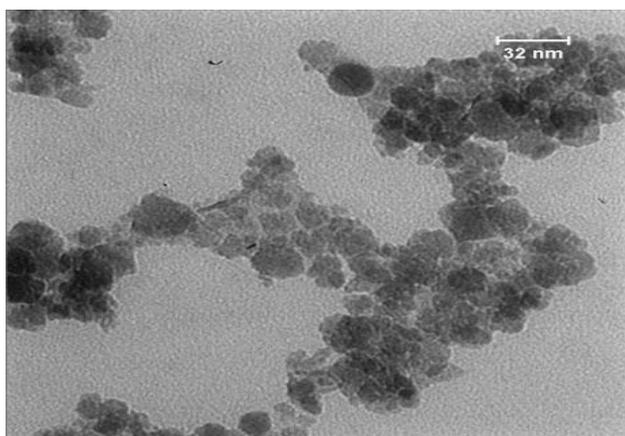


Figure 7. TEM image of the Ag/Fe₃O₄ MNPs

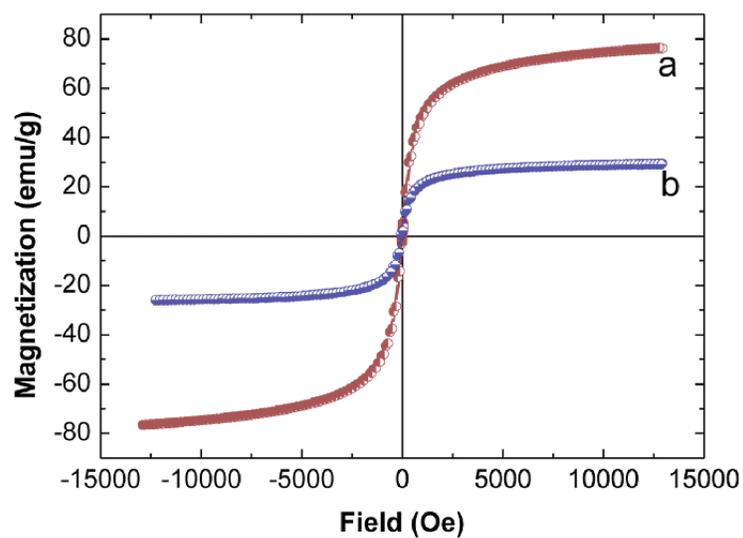


Figure 8. Magnetization loops of (a) Fe₃O₄ MNPs and (b) Ag/ Fe₃O₄ MNPs

Vibrating sample magnetometer (VSM) was used for the study magnetic property of catalyst at 300 °K by applying a magnetic field ranging from -15000 to 15000 Oe. The saturation magnetization (Ms) value Fe₃O₄ MNPs and Ag/Fe₃O₄ MNPs are 79.4 emu g⁻¹ and 22.5 emu g⁻¹, respectively. This experiment approves the superparamagnetic property of Ag/Fe₃O₄ MNPs and also confirmed that Ag coated well on the surface of Fe₃O₄ MNPs (Figure 8).

Conclusion

The results of this research showed that *Rosa Canina* plant extract has the potential to regenerate iron and silver and is capable of synthesizing Ag/Fe₃O₄ nanocomposite, which was confirmed by different methods of nanocomposite synthesis. One of the advantages of this synthesis method is the use of plant extracts for nanocomposite synthesis, which is considered a green method and has advantages such as being environmentally friendly, cost-effective, simple, fast, and avoiding the presence of toxic solvents.

Acknowledgments

The authors acknowledge Ilam University, Ilam, Iran, for financial support of this work.

Disclosure Statement

No potential conflict of interest was reported by the authors.

Funding

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

Authors' contributions

All authors contributed to data analysis, drafting, and revising of the paper and agreed to be responsible for all the aspects of this work.

Orcid

Nasrin Pourbahar

<https://orcid.org/0000-0002-4689-2898>

Somayeh Sattari Alamdar

<https://orcid.org/0000-0002-0354-7453>

References

- [1]. Hekmat A., Saboury A.A., Divsalar A. *J. Biomed. Nanotechnol.* 2012, **8**:968 [Crossref], [Google Scholar], [Publisher]
- [2]. Kayode Awote O., Solomon Anagun O., Gideon Adeyemo A., Olamilekan Igbalaye J., Lawrence Ogun M., Kolawole Apete S., Oluwaranti Folami S., Esther Olalero F., Chidera Ebube S., Ishola Taofeeq M., Oluwapelumi Akinloye O. *Asian Journal of Green Chemistry*, 2022, **6**:284 [Crossref], [Google Scholar]
- [3]. Jayasree D., Sreebamol K.S., Gopinath A. *Asian Journal of Green Chemistry*, 2022, **6**:14 [Crossref], [Publisher]
- [4]. Shaikh R., Nayab J., Shaikh N. *Asian Journal of Green Chemistry*, 2021, **5**:313 [Crossref], [Publisher]
- [5]. Sengar M.S., Saxena S., Lakhani A., P. Satsangee S. *Asian Journal of Green Chemistry*, 2021, **5**:206 [Crossref], [Publisher]
- [6]. Mahdavi M., Ahmad M.B., Haron M.J. *Molecules*, 2013, **18**:7533 [Crossref], [Google Scholar], [Publisher]
- [7]. Gao Z., Liu X., Deng G., *Dalton Trans*, 2016, **45**: 13456 [Crossref], [Google Scholar], [Publisher]
- [8]. Maleki-Ghaleh H., Aghaie E., Nadernezhad A., *J. Mater. Eng. Perfrom.*, 2016, **25**: 2331 [Crossref], [Google Scholar], [Publisher]

- [9]. Huang S., Li C., Cheng Z., *J. Colloid Interf. Sci.*, 2012, **376**:312 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [10]. Mondal K., Lorethova H., Hippo E., Wiltowski T., Lalvani S.B. *Fuel. Process Technol.*, 2004, **86**:33 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [11]. Cain J.L., Harrison S.R., Nikles J.A., Nikles D.E. *J. Magn. Magn. Mate.*, 1996, **155**:67 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [12]. Nasser M.A., Shahabi M., Allahresani A., Kazemnejadi M. *Asian Journal of Green Chemistry*, 2019, **3**:382 [[Crossref](#)], [[Publisher](#)]
- [13]. Mohammadi R., Isazadeh M. *Asian Journal of Green Chemistry*, 2019, **3**:432 [[Crossref](#)], [[Publisher](#)]
- [14]. Sengar M.S., Saxena S., Lakhani A., Satsangee S.P. *Asian Journal of Green Chemistry*, 2021, **5**:206 [[Crossref](#)], [[Publisher](#)]
- [15]. Waifalkar P.P., Parit S.B., Chougale A.D., Sahoo S.C., Patil P.S., Patil P.B., *J. Colloid Interf. Sci.*, 2016, **482**:159 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [16]. Xu J.K., Zhang F.F., Sun J. J., Sheng J., Wang F., Sun M. *Molecules*, 2014, **19**:21506 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [17]. Karakoti A.S., Hench L.L., Seal S., *Jom*, 2006, **58**:77 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [18]. Slavin Y.N., Asnis J., Häfeli U.O., Bach H., *J Nanobiotechnol.*, 2017, **15**:65 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [19]. Azizian Shermeh O., Valizadeh J., Noroozifar M., Qasemi A., *J. Ilam Uni. Med. Sci.*, 2016, **24**:92 [[Google Scholar](#)], [[Publisher](#)]
- [20]. Kulkarni S, Jadhav M, Raikar P, Barretto DA, Vootla SK, Raikar US. *New J Chem.* 2017, **41**:9513 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [21]. Huang L., Weng X., Chen Z., Megharaj M., Naidu R., *Spectrochim. Acta. Mol. Spectros.*, 2014, **117**:801 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [22] Cai W., Wan J.Q., *J Colloid Interface Sci.*, 2007, **305**:366 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]
- [23]. Shahwan T., Sirriah S.A., Nairat M., Boyaci E., Eroglu A.E., Scott T.B., *Chem. Eng. J.*, 2011, **172**:258 [[Crossref](#)], [[Google Scholar](#)], [[Publisher](#)]

How to cite this manuscript: Nasrin Pourbahar*, Somayeh Sattari Alamdar. Phytofabrication, and Characterization of Ag/Fe₃O₄ Nanocomposite from *Rosa Canina* Plant Extracts Using a Green Method. *Asian Journal of Green Chemistry*, 7(1) 2023, 9-16. DOI: 10.22034/ajgc.2023.1.2